


Client's name / Tên khách hàng : CB HITECH CO., LTD
Client's address / Địa chỉ : TẦNG 4, BẢO HIỂM QUÂN ĐỘI MIC, SỐ 8 PHẠM HÙNG, CẦU GIẤY, HÀ NỘI, VIỆT NAM

The following sample(s) was/were submitted and identified by the client as:


Các thông tin nhận dạng mẫu do khách hàng cung cấp:

Name of sample / Tên mẫu : JUPITER GREY
Quantity / Số lượng mẫu : 01 sample / mẫu
Date of receiving / Ngày nhận mẫu : 10-Apr-2018
Time of testing / Thời gian thử nghiệm : From / từ 10-Apr-2018 to / đến 26-Apr-2018
Test result / kết quả thử nghiệm : See next page(s) / Xem trang sau

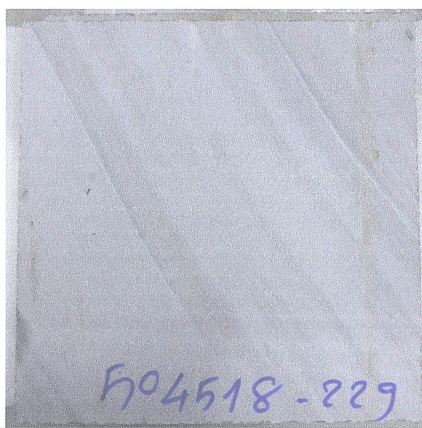

SGS authenticate the photos on original report only / SGS chỉ xác thực các hình ảnh trong báo cáo chính thức

Signed for and on behalf of
SGS Vietnam LTD

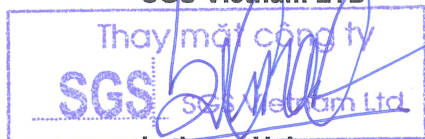

Le Long Hai
Construction Lab Manager
Industrial Services

005909

"This document is issued by the Company under its General Conditions of Service printed overleaf, available on request or accessible at <http://www.sgs.vn/en/terms-and-conditions> and for electronic format documents, subject to Terms and Conditions for Electronic Documents at <http://www.sgs.vn/en/terms-and-conditions/terms-e-document>. Attention is drawn to the limitations of liability, indemnification and jurisdiction issues defined therein. Any holder of this document is advised that information contained hereon reflects the Company's findings at the time of its intervention only and within the limits of Client's instructions, if any. The Company's sole responsibility is to its Client and this document does not exonerate parties to a transaction from exercising all their rights and obligations under the transaction documents. This document cannot be reproduced except in full, without prior written approval of the Company. Any unauthorized alteration, forgery or falsification of the content or appearance of this document is unlawful and offenders may be prosecuted to the fullest extent of the law. Unless otherwise stated the results shown in this test report refer only to the sample(s) tested only."

Characteristic <i>Tên chỉ tiêu</i>	Unit <i>Đơn vị</i>	Test methods <i>Phương pháp thử nghiệm</i>	Test result <i>Kết quả thử nghiệm</i>
1. Bulk specific gravity in dry condition <i>Khối lượng riêng ở trạng thái khô</i>	g/cm ³	ASTM C97 - 15	2.74
2. Compressive strength <i>Cường độ nén</i>	MPa	ASTM C170 - 16	144.7
3. Modulus of rupture <i>Môđun phá hủy</i>	MPa	ASTM C99 - 15	18.5
4. Water absorption <i>Độ hút nước</i>	%	ASTM C97 - 15	0.1
5. Flexural strength <i>Cường độ uốn</i>	MPa	ASTM C880 - 15	17.0
6. Flexural modulus of elasticity <i>Môđun đàn hồi uốn</i>	MPa	ASTM C1352 - 15	16840
7. Abrasion resistance (*) <i>Độ chịu mài mòn</i>	cm ³	ASTM C1353 - 15a	38.6

Note:

- (*) Test conditions / *Điều kiện thử nghiệm*: 22 ± 3 °C; 50 ± 5 %.
Type of abrasive wheel / *Loại bánh mài*: H-22.
Load applied to the abrasive wheels (per arm) / *Tải trọng áp dụng cho bánh mài*: 1000g.
Number of cycles / *Số chu kỳ*: 1000 cycles.

★★★ END OF THE REPORT ★★★

"This document is issued by the Company under its General Conditions of Service printed overleaf, available on request or accessible at <http://www.sgs.vn/en/terms-and-conditions> and for electronic format documents, subject to Terms and Conditions for Electronic Documents at <http://www.sgs.vn/en/terms-and-conditions/terms-e-document>. Attention is drawn to the limitations of liability, indemnification and jurisdiction issues defined therein. Any holder of this document is advised that information contained hereon reflects the Company's findings at the time of its intervention only and within the limits of Client's instructions, if any. The Company's sole responsibility is to its Client and this document does not exonerate parties to a transaction from exercising all their rights and obligations under the transaction documents. This document cannot be reproduced except in full, without prior written approval of the Company. Any unauthorized alteration, forgery or falsification of the content or appearance of this document is unlawful and offenders may be prosecuted to the fullest extent of the law. Unless otherwise stated the results shown in this test report refer only to the sample(s) tested only."